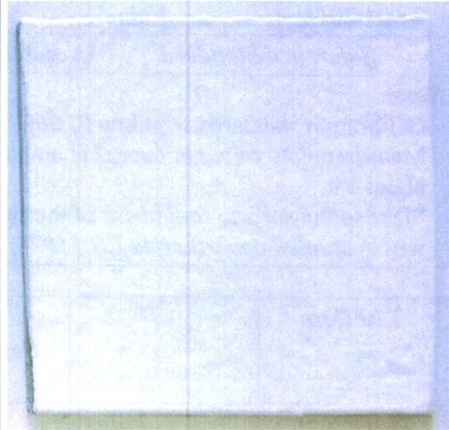


Sample Id. 0114_01032016	<b>TEST REPORT N° ETR-16-0060</b>	Page 1/2
-----------------------------	-----------------------------------	-------------

### GENERAL INFORMATION

<b>Subject:</b>	Test report on testing activities to determine solar reflectance, infrared emittance and solar reflectance index (SRI).		
<b>Client</b>	AMA Composites Srl Via Repubblica 7 42011 Campogalliano (MO) P.IVA: 02905040362	<b>Client reference person</b>	Marco Corradini Phone +39.059.851754 Email info@amacomposites.it
<b>Commitment document</b>	-	<b>Report release date</b>	22/04/2016

### SAMPLE DATA

<b>Receipt date</b>	01/03/2016			 Sample picture
<b>Sample id. sub.</b>	-			
<b>ECRC id</b>	-			
<b>Manufacturer</b>	-			
<b>Product name</b>	Thermogel Outside			
<b>Sampling</b>	Supplied by the Client			
<b>Short physical description*</b>	Product type: aerogel water based paint with heat reflecting properties Substrate: bituminous membrane			
<b>Sample thickness</b>	4.1 mm	<b>Total sample size</b>	300 x 210 mm	
<b>Surface coated</b>	YES	<b>Coating thickness</b>	N.A.	
<b>Surface state</b>	<i>variegated</i> NO	<i>aged</i> NO	<i>cleaned</i> NO	
<b>Information on history and ageing*</b>	N.A.			
<b>Optical properties</b>	Diffusive reflecting	NO		
	Specular reflecting	NO		
	Intermediate reflecting	YES		
	Clear transmitting	NO		
	Translucent transmitting	NO		
	Opaque	YES		
<b>Notes</b>	Information on surface coating, aging and cleaning provided by the Client where known.			

The test results are based on the material supplied by the client. This report shall not be reproduced except in full without the written approval of this laboratory. This laboratory assumes no responsibility nor makes a performance or warranty statement for this material or products and processes containing this material in connection with this report.

Sample Id. 0114_01032016	<b>TEST REPORT N° ETR-16-0060</b>	Page 2/2
-----------------------------	-----------------------------------	-------------

### TEST RESULTS

Test Date		Solar Reflectance (SR)	Standard Deviation	Measured Values		
7/03/2016	Value	0.859	0.002	0.857	0.859	0.861
<b>Reference Standard</b>		ASTM C1549-09				
<b>Reference Solar Spectrum</b>		ASTM Standard G173 Hemispherical Tilt				

**Notes**

This test was performed according to *ASTM C1549-09: Standard Test Method for Determination of Solar Reflectance Near Ambient Temperature Using a Portable Reflectometer* with air mass 1.5. A solar spectrum reflectometer Devices and Services SSR-ER was used. Calibration standards with low (0.000) and high (0.864) solar reflectance were provided by the instrument manufacturer.

Measurements were conducted at ambient temperature of  $22 \pm 4^\circ\text{C}$  and relative humidity of  $41\% \pm 10\%$ .

Test Date		Infrared Emittance (IE)	Standard Deviation	Measured Values				
21/04/2016	Value	0.890*	0.002	0.891	0.892	0.889	0.889	0.890
<b>Reference Standard</b>		Not Accredited Slide Method- Not Accredited EN 15976						

**Notes**

Calibration standards with low (0.060) and high (0.870) emittance were provided by the instrument manufacturer. Measurements were conducted at ambient temperature of  $22 \pm 4^\circ\text{C}$  and relative humidity of  $41\% \pm 10\%$  in a time period of about 1 h.

\*Due to the surface roughness of the sample, it was not possible to measure IE according to *ASTM C1371: Thermal Emittance was evaluated according to EN 15976, non-accredited method.*

Test Date		Solar Reflectance (SR)	Infrared Emittance (IE)	Solar Reflectance Index (SRI) [%]		
				Low wind	Medium wind	High Wind
21/04/2016	Value	0.859	0.890*	109.1	108.3	107.9
				Surface temperature (ST) [°C]		
				44.3	41.5	39.2
<b>Reference Standard</b>		ASTM E1980-11*				

**Notes**

This calculation was performed according to *ASTM E1980-11: Standard Practice for Calculating Solar Reflectance Index of Horizontal and Low-Sloped Opaque Surfaces*. This utilizes the following values for the convection coefficient:  $h_c = 5 \text{ W/m}^2\cdot\text{K}$  for low-wind (0 to 2 m/s),  $h_c = 12 \text{ W/m}^2\cdot\text{K}$  for medium-wind (2 to 6 m/s), and  $h_c = 30 \text{ W/m}^2\cdot\text{K}$  for high-wind (6 to 10 m/s).

\*Since it was not possible to measure IE according to *ASTM C1371, Thermal Emittance was evaluated according to EN 15976, non-accredited method.*

The Responsible of EELab Laboratory

Prof. Alberto Muscio

